

Milomirka Škrba^{1*}, Zoran Obrenović^{1,2}, Aleksandar Došić¹,
Miladin Gligorić¹, Biljana Đurić², Ivan Savić³

¹University of East Sarajevo, Faculty of Technology Zvornik,
Zvornik, Republic of Srpska, Bosnia and Herzegovina, ²Alumina
doo, Zvornik, Republic of Srpska, Bosnia and Herzegovina,

³University of Niš, Faculty of Technology in Leskovac, Leskovac,
Republic of Serbia

Scientific paper

ISSN 0351-9465, E-ISSN 2466-2585

UDC: 661.183.6:544.726:546.131

<https://doi.org/10.5937/zasmat2103155S>



Zastita Materijala 62 (3)
155 - 165 (2021)

Ion exchange of sodium with hydrochloric acid in ZSM-5 zeolite

ABSTRACT

ZSM-5 zeolites are highly silicate materials that have significant application in catalytic processes in petrochemistry, especially due to their high selectivity. Most reactions in the petrochemical industry are acid-catalyzed. The acidic properties of zeolite depend on the number of acid centers, i.e. the presence of hydrogen ions, and therefore, in this paper the possibility of reducing the sodium content in the pores of high silicate zeolite ZSM-5 with the modulus ($\text{SiO}_2 / \text{Al}_2\text{O}_3 = 1000$) will be investigated, by applying ion exchange with hydrochloric acid. Chemical analysis of samples before and after ion exchange, and application of instrumental methods of X-Ray diffraction, FT-IR spectroscopy, and SEM analysis monitored the influence of the quantity of hydrogen ions on the chemical composition and the structure of ZSM-5 zeolite at different acid concentrations and at different exchange times.


It has been shown that the application of ion exchange with hydrochloric acid can reduce the sodium content in zeolite. Even with the application of 5% HCl for 6 hours, the content of sodium in the zeolite is reduced by over 98%. A similar effect is achieved by applying more concentrated hydrochloric acid solutions for a shorter ion exchange time. By prolonging the ion exchange time, there are no significant changes in terms of the final ion exchange. On the other hand, the application of HCl solutions of higher concentrations leads to a slight decrease in the aluminum content in the zeolite, which may partially affect the structural stability of the zeolite. The results obtained by FT-IR and SEM analysis and X-Ray diffraction confirm the possibility of ion exchange with hydrochloric acid, without significant changes in the crystal structure of the zeolite.

Keywords: zeolite, sodium ion exchange, characterization of H-ZSM-5, XRD, FT-IR, SEM.

1. INTRODUCTION

Zeolites are crystalline aluminosilicates composed of an ordered system of channels and cavities. The crystal lattice of zeolite is built of TO_4 tetrahedra, where T represents the Al^{3+} or Si^{4+} ion(s), interconnected by oxygen atoms [1-3]. Since the silicon atom has four valence electrons, SiO_4 tetrahedra are electroneutral, but when the Si^{4+} ion is replaced with Al^{3+} in the center of the tetrahedron, the crystal lattice becomes negatively charged. The negative charge of the lattice is neutralized by cations of alkali and alkaline earth metals, or hydrogen ions, located in the pore openings [4,5].

The chemical composition of the zeolite can be represented by following the formula [6,7]:



where:

M - extra-framework cation (Na, K, Li) and/or (Ca, Mg, Ba, Sr),

n - cation charge,

x - number of aluminium atoms,

y - number of silicon atoms, and

p - number of water molecules in each unit cell; $y/x = 1-6$, $p/x = 1-4$.

Zeolites of the ZSM type (*Zeolite Socony Mobil* or *Zeolite Sieve of Molecular porosity*) belong to the group of MFI zeolites, and they have the largest application in the petrochemical industry as catalysts and adsorbents. The crystal lattice of these high silicate materials consists of two types of three-dimensional channels whose openings are

Corresponding author: Milomirka Škrba

E-mail: milomirka.skrba@tfzv.ues.rs.ba

Paper received: 14. 04. 2021.

Paper accepted: 28. 05. 2021.

Paper is available on the website: www.idk.org.rs/journal

the size of 10-membered rings. The first channels are straight and elliptical (0.51 x 0.57 nm in diameter), while the second intersect the right channels at right angles, and they are sinusoidal and circular in cross-section (0.54 x 0.56 nm in diameter) [8-10].

Zeolites are the most important inorganic cation ion exchangers in which the crystallographic positions of the cations affect the rate and mechanism of ion exchange. Because extra-framework cations are bound by weak electrostatic forces to water molecules or structural atoms of silicon or aluminum, they are extremely mobile and can be easily exchanged in ion exchange processes without disturbing the crystal structure. However, this also depends on the chemical composition and crystal structure of a particular zeolite [11-14].

Since ZSM-5 zeolite, is mostly used in the petrochemical industry [15], especially in hydrocracking reactions, due to its catalytic action, it is important to provide a sufficient amount of acid sites to improve their catalytic action. The number and quantity of Brønsted and Lewis acid centers, as well as their ratio, affect the acid-base properties of zeolites. In addition, the catalytic activity and selectivity of ZSM-5 zeolite depend on the chemical composition of the starting materials for synthesis, degree of crystallinity, temperature and crystallization time, type of template, and many other factors [9,16,17].

2. EXPERIMENTAL PART

ZSM-5 zeolite with a molar ratio of $\text{SiO}_2/\text{Al}_2\text{O}_3 = 1000$, from the *Plant for the production of special zeolites*, was used as a starting sample, where amorphous silica, with particle size distribution up to 80 μm , is most often used as a source of silicon, and sodium -aluminate is used as a source of aluminum, in powder form. The synthesis of ZSM-5 zeolites mostly involves the use of the so-called templates that fill the space in the zeolite structure, to direct the upbuilding of the crystal lattice during the crystallization process or as charge stabilizers in the zeolite structure, and can also affect the kinetics of zeolite synthesis [16]. In this case, tetrapropylammonium bromide (TPABr) was used as a template. During each synthesis, a certain amount of previously produced zeolite without specific characteristics is added, to act as a crystallization germ, as well as a certain amount of water glass, which also contains a significant percentage of silicon, and caustic soda, which provides alkalinity of the reaction medium.

The initial zeolite sample was calcined to 550°C. The ion exchange process of ZSM-5 zeolite was performed in the *Alumina Research Laboratory*. A 20% suspension of calcined zeolite and hydrochloric acid was prepared, and then stirred on a magnetic stirrer at 90 °C for 1, 3, and 6 hours. Hydrochloric acid concentrations ranged from 5 to 15%. In the ion exchange reaction, Na^+ ions were exchanged with H^+ ions.

After ion exchange was completed, vacuum filtration was performed and the filter cake was rinsed. The sample was then dried at 105 °C in an oven. The loss on ignition was determined according to the standard method *ISO 6606/1986*.

Multi - elemental analysis of the concentrations of metals was used for the chemical analysis of samples, i.e. determination of changes in metal contents, using the *ICP - OES SPEKTROGENESIS* device. The determination of the content of individual metals was carried out according to the standard method *EN-ISO 11885*.

The structural characteristics of the zeolite samples were determined using diffractograms recorded on an X-ray diffractometer *BRUKER D4 ENDEAVOR* with an X-ray tube, and a copper anticathode, using $\text{CuK}\alpha$ radiation at the wavelength $\lambda = 1.54060 \text{ \AA}$. By comparing the areas of peaks that are characteristic of the ZSM-5 zeolite standard with a modulus of 400, i.e. the standard values from the crystallographic base of the laboratory, and the tested samples with a modulus of 1000, the degree of crystallinity of the sample was quantified. The degree of crystallinity of zeolite samples was determined according to the standard test method *ASTM D5758-1*.

In addition to X-ray diffraction (XRD), structural changes, as well as reactions within the pores of zeolite can be observed using FT-IR spectroscopy (*Fourier - transform infrared spectroscopy*). For the purpose of the present study, the FT-IR spectrometer *SHIMADZU* was used. The recording was performed in the range of 500 to 4000 cm^{-1} .

Changes in the morphological characteristics of the zeolite samples were monitored using scanning electron microscopy (SEM) on the *MIRA3 TESCAN* device, at a voltage of 20 kV, and a magnification of 10 000 times.

3. RESULTS AND DISCUSSION

Table 1 shows the results obtained by chemical analysis of the samples of non-calcined and calcined zeolite ZSM-5 with the $\text{SiO}_2 / \text{Al}_2\text{O}_3$ ratio of 1000.

Table 1. Chemical composition of the starting sample of non-calcined and calcined ZSM-5 zeolites

Tabela 1. Hemijski sastav polaznog uzorka nekalcinisanog i kalcinisanog ZSM-5 zeolita

Sample	Loss on ignition [%]	%Na	%Al ₂ O ₃	%SiO ₂
non-calcined ZSM-5	13.60	1.03	0.17	98.06
calcined ZSM-5	3.98	1.11	0.20	98.14

Calcination of ZSM-5 zeolite at 550 °C removes the used TPABr template and crystal water, as a result of which the loss on ignition is significantly

reduced, while the content of sodium, aluminium, and silicon does not change significantly (Table 1).

Table 2. The effect of ion exchange time and HCl concentration on sodium and Al₂O₃ contentsTabela 2. Uticaj vremena jonske izmjene i koncentracije HCl na sadržaj natrijuma i Al₂O₃

Sample	Ion exchange time [h]	Acid concentration [%]	Loss on ignition [%]	%Na	%Al ₂ O ₃
ZSM-5 5% HCl 6h	6	5	0.61	0.019	0.17
ZSM-5 7% HCl 6h	6	7	0.64	0.012	0.15
ZSM-5 10% HCl 1h	1	10	0.76	0.018	0.15
ZSM-5 10% HCl 3h	3	10	0.76	0.014	0.14
ZSM-5 10% HCl 6h	6	10	0.59	0.010	0.13
ZSM-5 12% HCl 6h	6	12	0.62	0.014	0.13
ZSM-5 15% HCl 1h	1	15	1.00	0.021	0.13
ZSM-5 15% HCl 3h	3	15	0.83	0.016	0.12
ZSM-5 15% HCl 6h	6	15	0.62	0.012	0.11

As can be seen from the data shown in Table 2 and Figure 1, the action of hydrochloric acid, of different concentrations, on the initial calcined zeolite sample results in the exchange of sodium ions with hydrogen ions. With sodium ion exchange already with 5% HCl, at a change time of 6 hours, there is a significant reduction in the sodium

content of the zeolite of over 98%. With a more concentrated HCl solution, at a change time of 6 h, there are no significant changes in terms of the final ion exchange of sodium, i.e. the reduction of the sodium content in the zeolite is certainly over 98%.

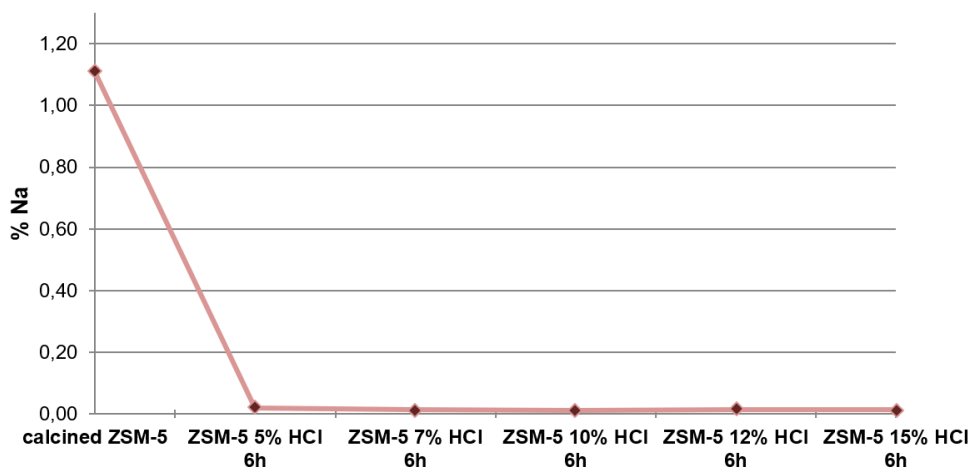


Figure 1. The ion exchange of sodium with hydrochloric acid of different concentrations

Slika 1. Jonska izmjena natrijuma sa hlorovodoničnom kiselinom različitih koncentracija

Figures 2 - 3 show the influence of ion exchange time on the reduction of the sodium content in zeolite, and it can be seen that the process of sodium ion exchange with hydrogen ions is extremely efficient, already at an ion

exchange time of 1 hour, with 10% and 15% HCl. By further prolonging the ion exchange time, there are no significant changes in the sodium content in the zeolite (Table 2).

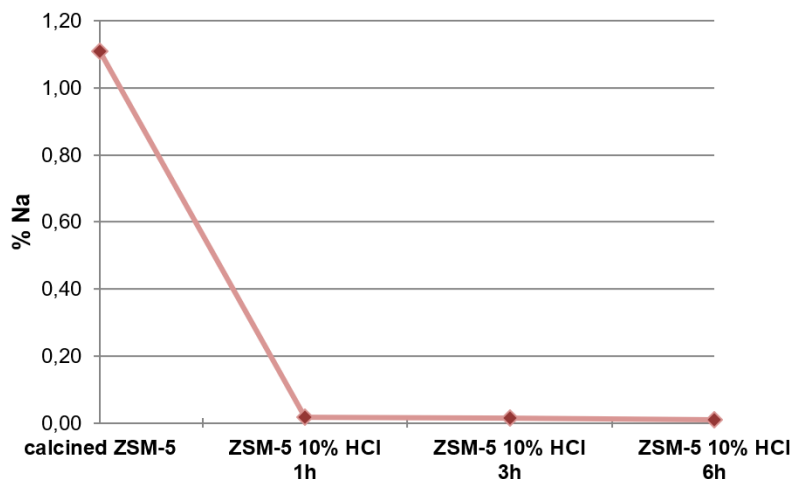


Figure 2. The ion exchange of sodium with 10% HCl for varying exchange times

Slika 2. Jonska izmjena natrijuma pri različitim vremenima jonske izmjene sa 10% HCl

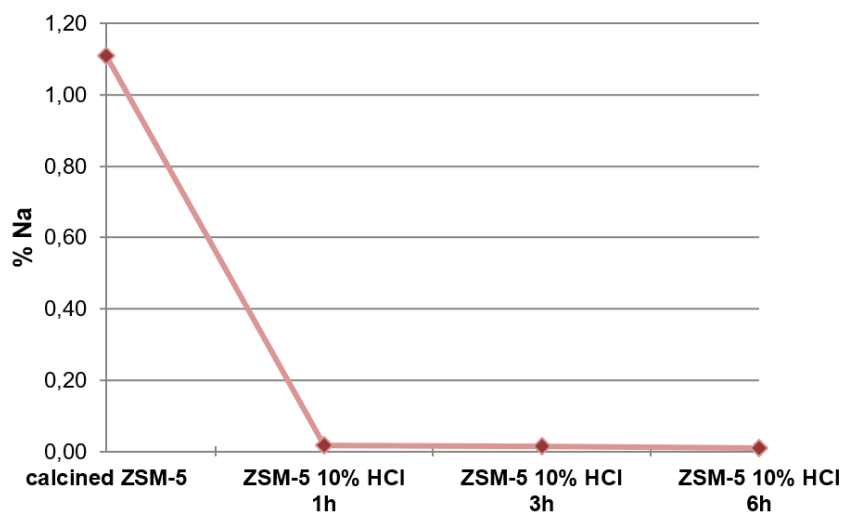


Figure 3. The ion exchange of sodium with 15% HCl for varying exchange times

Slika 3. Jonska izmjena natrijuma pri različitim vremenima jonske izmjene sa 15% HCl

In the case of ion exchange with HCl, there is a slight decrease in the aluminium content at lower concentrations of acid, because the acid is mostly spent on the exchange of sodium ions (Figure 4). Figure 4 shows the effect of HCl concentration on the reduction of the aluminium content in zeolite during ion exchange. It is evident that increasing the HCl concentration slightly reduces the aluminium content in the zeolite after ion exchange;

however, this can affect the structural stability of the zeolite itself.

Figures 5 and 6 show the effect of HCl ion exchange time on the reduction of aluminium content in the zeolite with 10 %HCl and 15% HCl. During the ion exchange, the aluminium content decreases, with HCl combining with the aluminium from the zeolite crystal lattice, as a result of which the aluminium is partially removed in the form of chloride.

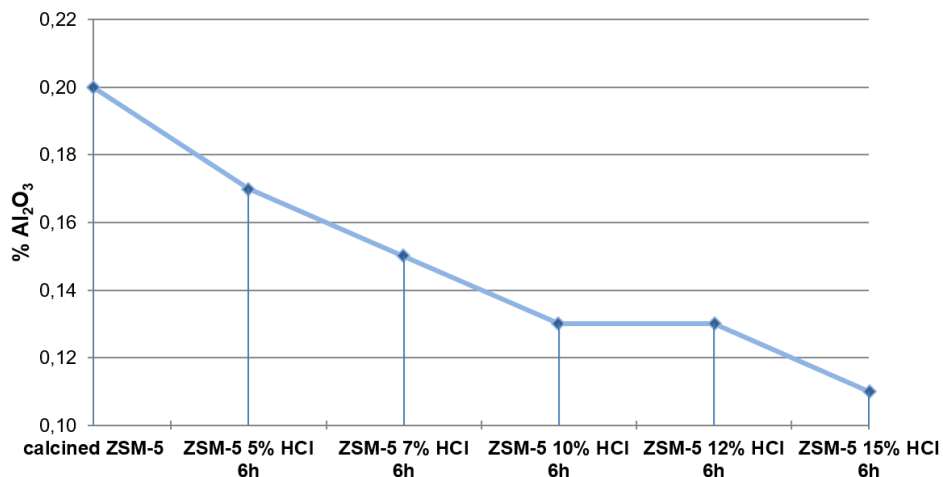


Figure 4. Change in Al₂O₃ content at different concentrations of hydrochloric acid
Slika 4. Promjena sadržaja Al₂O₃ pri različitim koncentracijama hlorovodonične kiseline

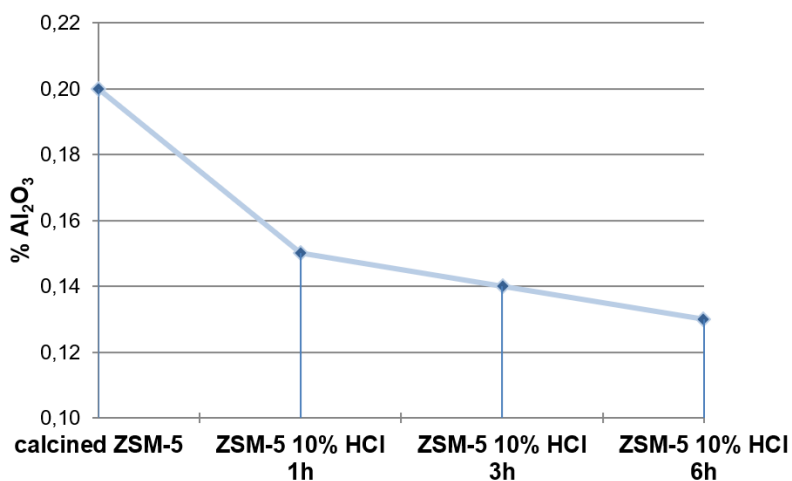


Figure 5. Change in Al₂O₃ content at different ion exchange times with 10% HCl
Slika 5. Promjena sadržaja Al₂O₃ pri različitim vremenima jonske izmjene sa 10% HCl

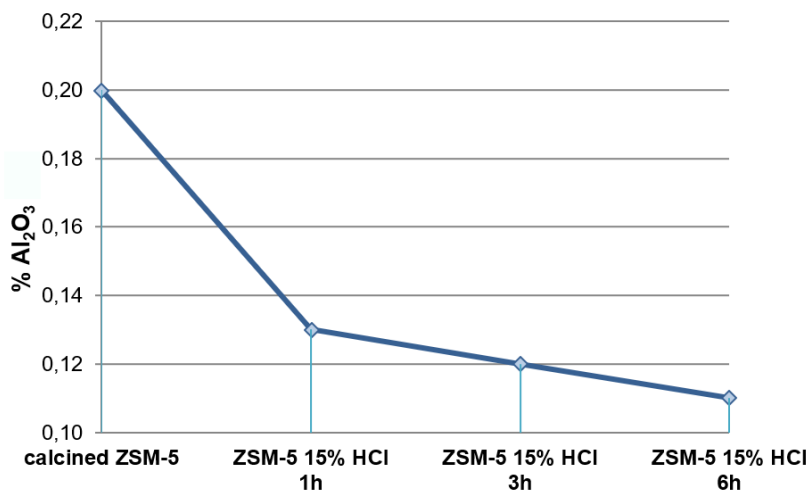


Figure 6. Change in Al₂O₃ content at different ion exchange times with 15% HCl
Slika 6. Promjena sadržaja Al₂O₃ pri različitim vremenima jonske izmjene sa 15% HCl

By comparing the obtained FT-IR spectra for non-calcined and calcined zeolite, certain changes in the intensity of the characteristic peaks for zeolites can be observed (Figure 7). Absorption bands occurring at wavenumbers 788, 1084, and 1218 cm^{-1} correspond to the presence of tetrahedral SiO_4 units. With calcined zeolite, more intense peaks are obtained at wavenumbers of 543 cm^{-1} (vibrations due to stretching of external bonds of AlO_4 and SiO_4 tetrahedra), and 1084 cm^{-1} (internal asymmetric vibrations of Si-O-T bonds), which may be due to higher stresses in the crystal lattice, due to the removal of templates and crystal water by the calcination process. The intensities of the absorption bands at a wavenumber of 788 cm^{-1} (symmetrical stretching of external bonds that maintain the structure) and 1218 cm^{-1} (asymmetric

stretching, vibrations of external bonds in structures containing, so-called pentasil, present in ZSM-5 zeolite) are reduced in the calcined zeolite. At a wavenumber of 1621 cm^{-1} , an exothermic process takes place, which refers to water desorption, and the intensity of the absorption band at that wavenumber is lower in calcined zeolite due to the vibration reductions of the H-OH bond [9,18,19].

Calcination partially removes TPABr templates, which is evident from the decrease in the intensity of the absorption band in the wavenumber range 3431 - 3625 cm^{-1} . In addition, the doublet occurring at 2330 and 2340 cm^{-1} indicates CO_2 formation, upon complete oxidation of the propyl chains of TPA^+ molecules [9,20].

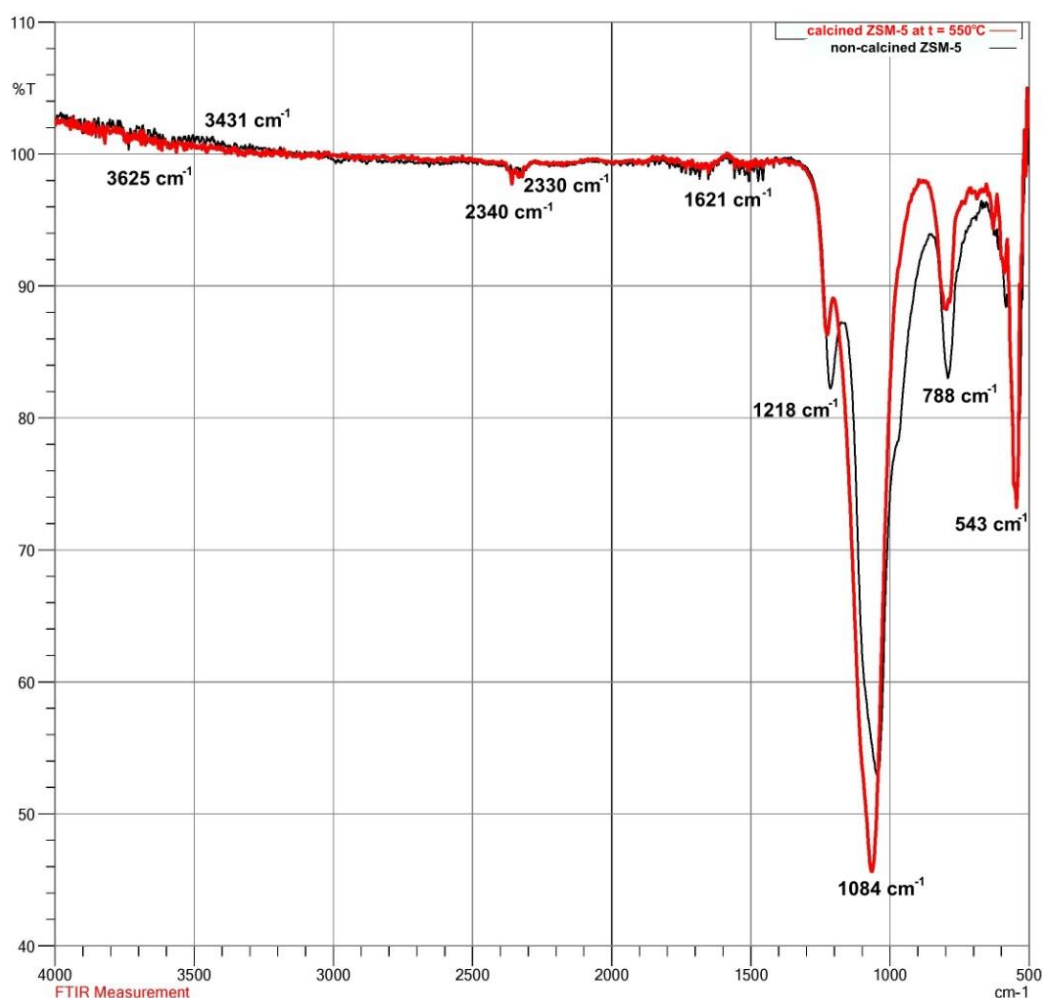


Figure 7. FT-IR spectra of non-calcined (-) and calcined (-) zeolite ZSM-5

Slika 7. FT-IR spektri nekalcinisanog (-) i kalcinisanog (-) zeolita ZSM-5

Based on the FT-IR spectra shown in Figure 8, the coincidence of the characteristic peaks of the analyzed samples of ZSM-5 zeolite modified with

HCl of different concentrations and the calcined sample of ZSM-5 zeolite can be observed.

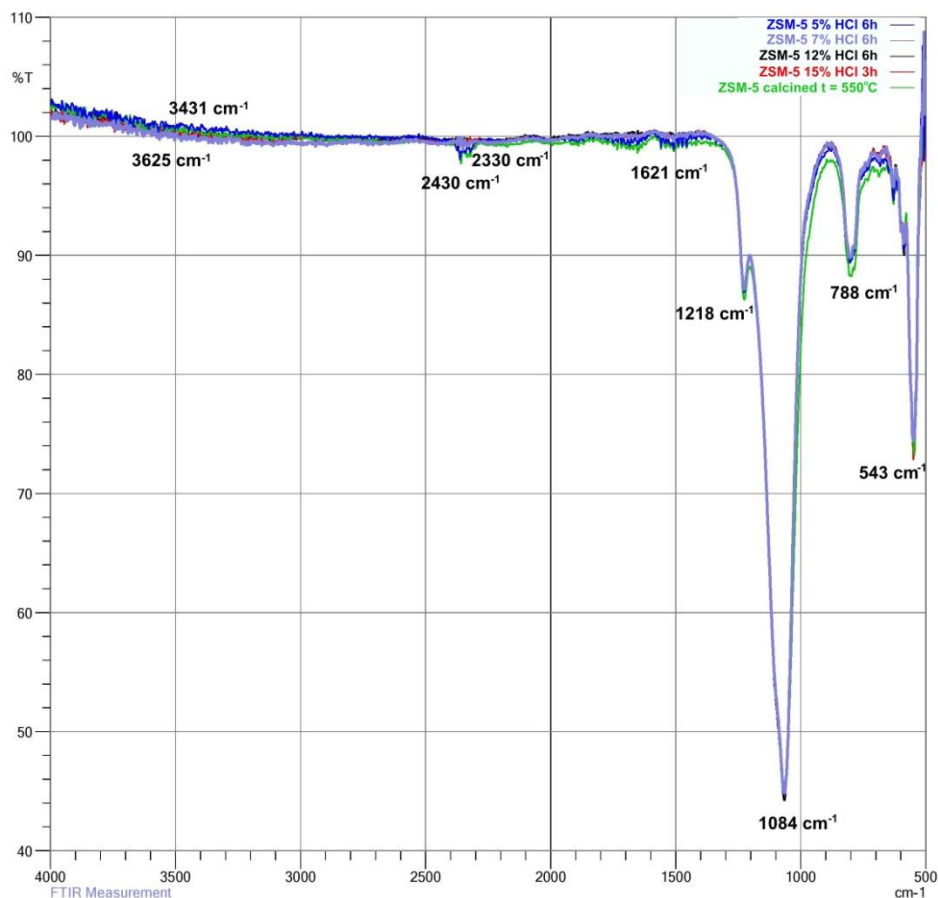


Figure 8. FT-IR spectra of different samples of ZSM-5 zeolite

Slika 8. FT-IR spektri različitih uzoraka zeolita ZSM-5

The structural characteristics of ZSM-5 zeolites were examined by X-Ray diffraction (Figures 9-10). The obtained peaks, in the range $2\theta = 22.7 - 25.1^\circ$, confirm the crystal structure of all analyzed samples of ZSM-5 zeolite [8, 16]. The quotient of the calculated areas below the peaks in the range $2\theta = 22.7 - 25.1^\circ$ for each sample separately and the calculated area below the peaks of the standard in the same range 2θ , gives the degree of crystallinity of the zeolite. Based on the obtained values of the degree of crystallinity in the stated range 2θ (Table 3), it can be noticed that the degree of crystallinity decreases with calcination because the degree of crystallinity decreases at a higher aluminium content [17].

The increase in aluminium content in calcined zeolite was also confirmed by the diffractogram in Figure 9a, because in the region $2\theta = 8.39 - 9.62^\circ$ there is a more intense peak in calcined zeolite, whose peak intensity corresponds to the presence of aluminium in the zeolite structure. On the other hand, the degree of crystallinity of ZSM-5 zeolite with the $\text{SiO}_2/\text{Al}_2\text{O}_3 = 1000$ modulus is higher than ZSM-5 zeolite with the $\text{SiO}_2/\text{Al}_2\text{O}_3 = 400$ modulus, which confirms the fact that increasing silicate modulus increases the degree of crystallinity [17].

Table 3. Comparison of the degree of crystallinity of ZSM-5 samples

Tabela 3. Poređenje stepena kristalichnosti uzoraka ZSM-5

Sample	Degree of crystallinity, [%]
non-calcined ZSM-5	108.69
calcined ZSM-5	94.83
ZSM-5 5% HCl 6h	91.57
ZSM-5 7% HCl 6h	95.51
ZSM-5 10% HCl 1h	95.13
ZSM-5 10% HCl 3h	90.29
ZSM-5 12% HCl 6h	95.51
ZSM-5 15% HCl 1h	89.58
ZSM-5 15% HCl 3h	90.54

XRD diffractograms for different samples of ZSM-5 zeolite, shown in Figure 9b, exhibit almost identical peaks, except that the zeolite modified with 15% HCl undergoes a significant reduction in peak intensities in the region of $2\theta = 22.7 - 25.1^\circ$. This is in accordance with the results shown in Tables 2 – 3. Besides, the peaks move along the 2θ axis to the diffractogram of calcined ZSM-5 zeolite, so that at lower acid concentrations, i.e.

with ion exchange with 5% and 7% HCl, the peaks move to the left, and in ZSM-5 zeolite with 15% HCl and at 3h exchange time, they move to the right. The XRD diffractogram of ZSM-5 zeolite at 5% HCl and 6h exchange time is shifted furthest to the left and indicates that the ion exchange process is dominant and that 5% HCl does not lead to the

destruction of the crystal structure of the zeolite. On the other hand, the XRD diffractogram of zeolite ZSM-5 15% HCl 3h was shifted furthest to the right, which is an indicator of the degradation of the crystal lattice in zeolite due to increased acid concentration, i.e. decreased degree of crystallinity (Table 3).

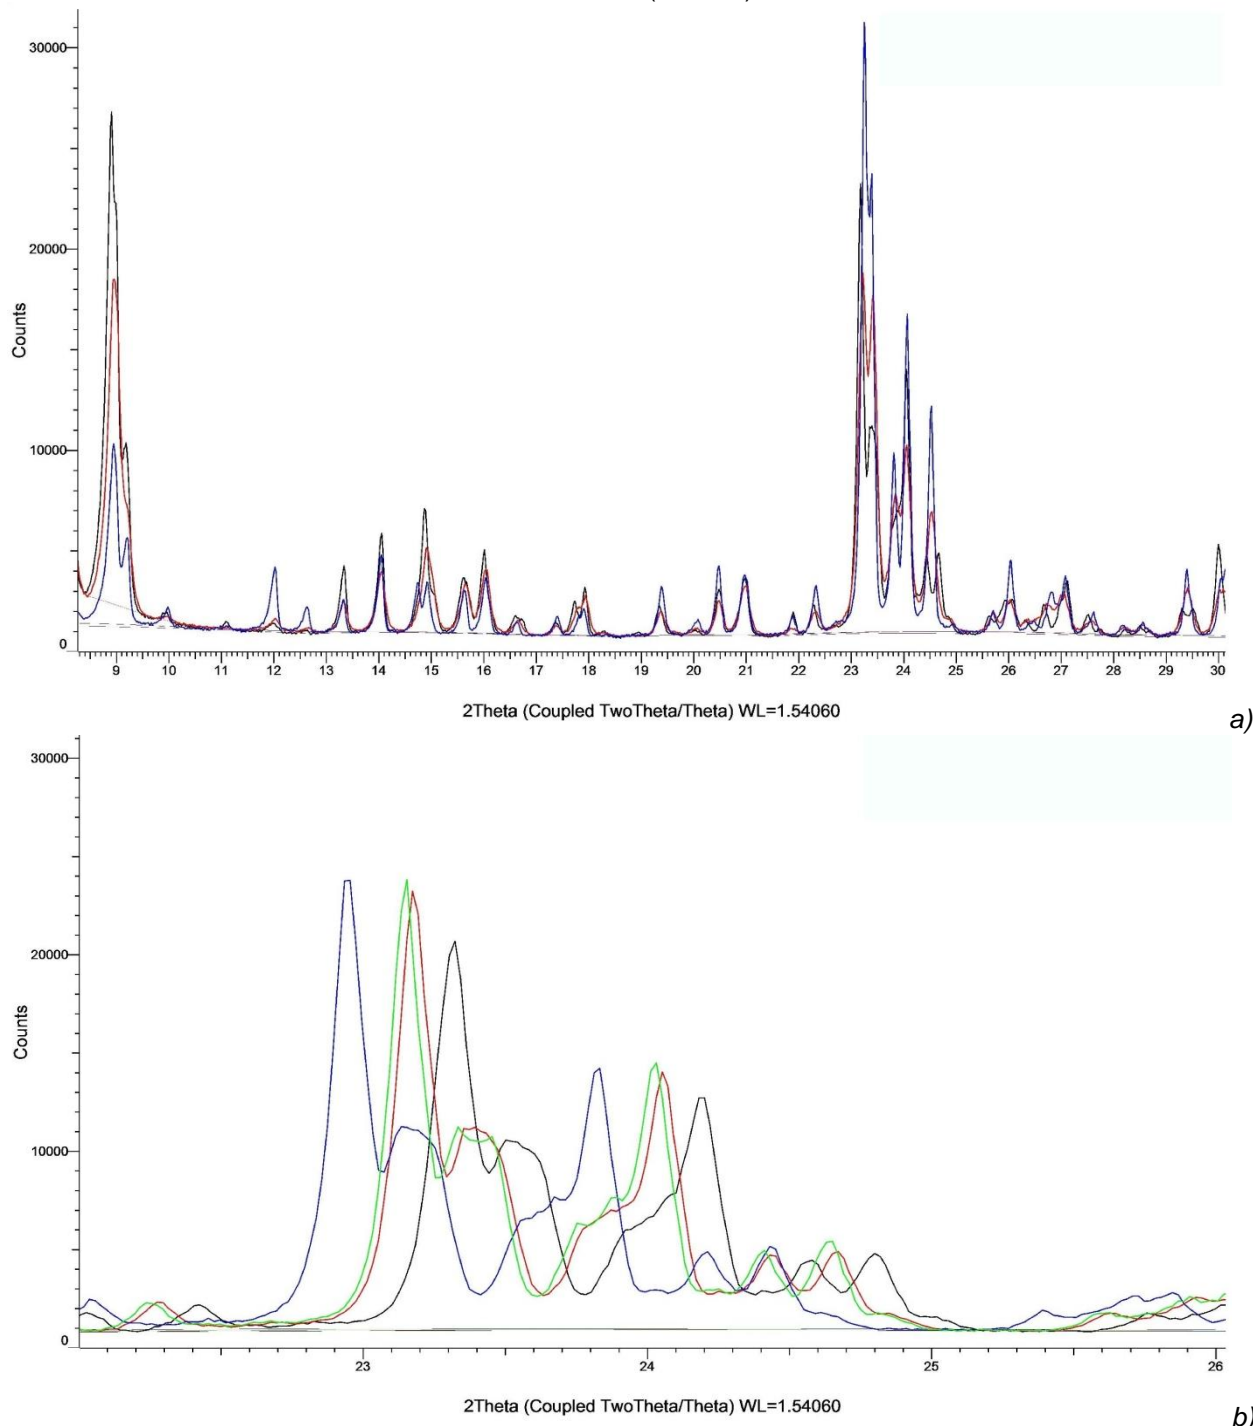


Figure 9. Comparison of XRD diffractograms: a) ZSM-5 standard (-), non-calcined (-) and calcined (-) ZSM-5, b) calcined ZSM-5 (-), ZSM-5 5% HCl 6h (-), ZSM-5 7% HCl 6h (-) and ZSM-5 15% HCl 3h (-)
 Slika 9. Poređenje XRD difraktograma: a) ZSM-5 standard (-), nekalcinirani (-) i kalcinirani (-) ZSM-5, b) kalcinirani ZSM-5 (-), ZSM-5 5% HCl 6h (-), ZSM-5 7% HCl 6h (-) i ZSM-5 15% HCl 3h (-)

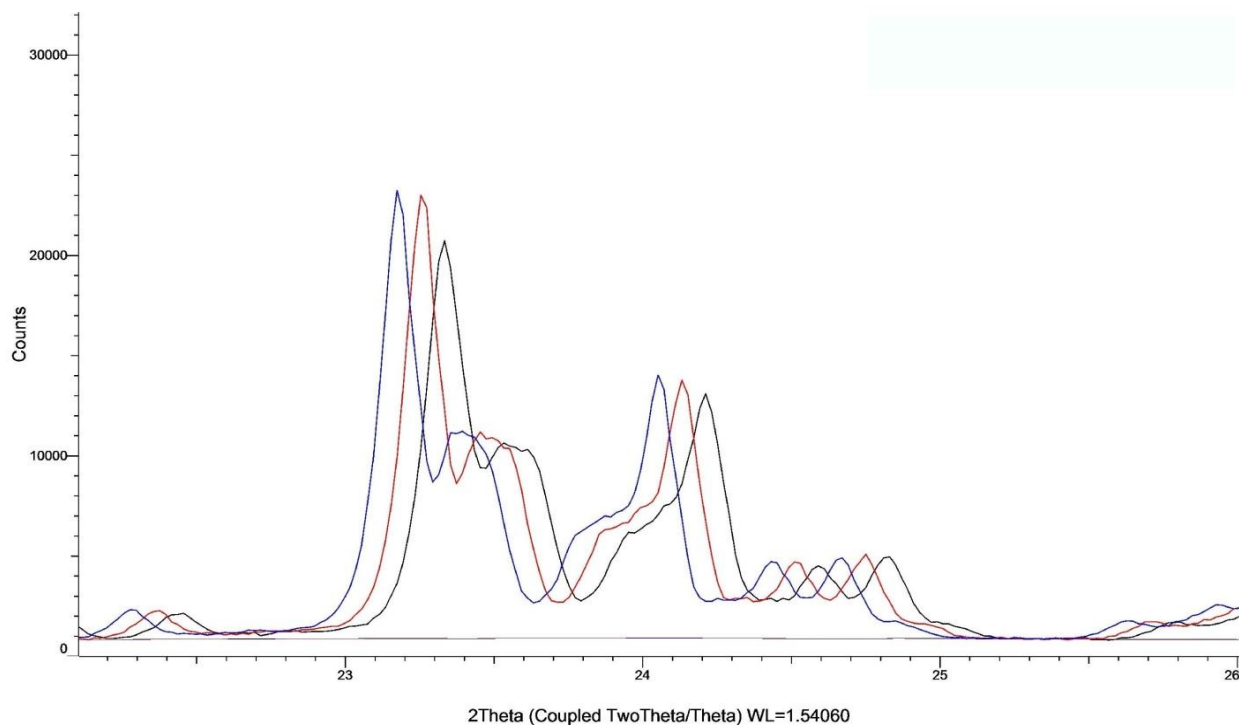


Figure 10. Comparison of XRD diffractograms: calcined ZSM-5 (-), ZSM-5 10% HCl 1h (-) and ZSM-5 10% HCl 3h (-)

Slika 10. Poređenje XRD difraktograma: kalcinisanog ZSM-5 (-), ZSM-5 10% HCl 1h (-) i ZSM-5 10% HCl 3h (-)

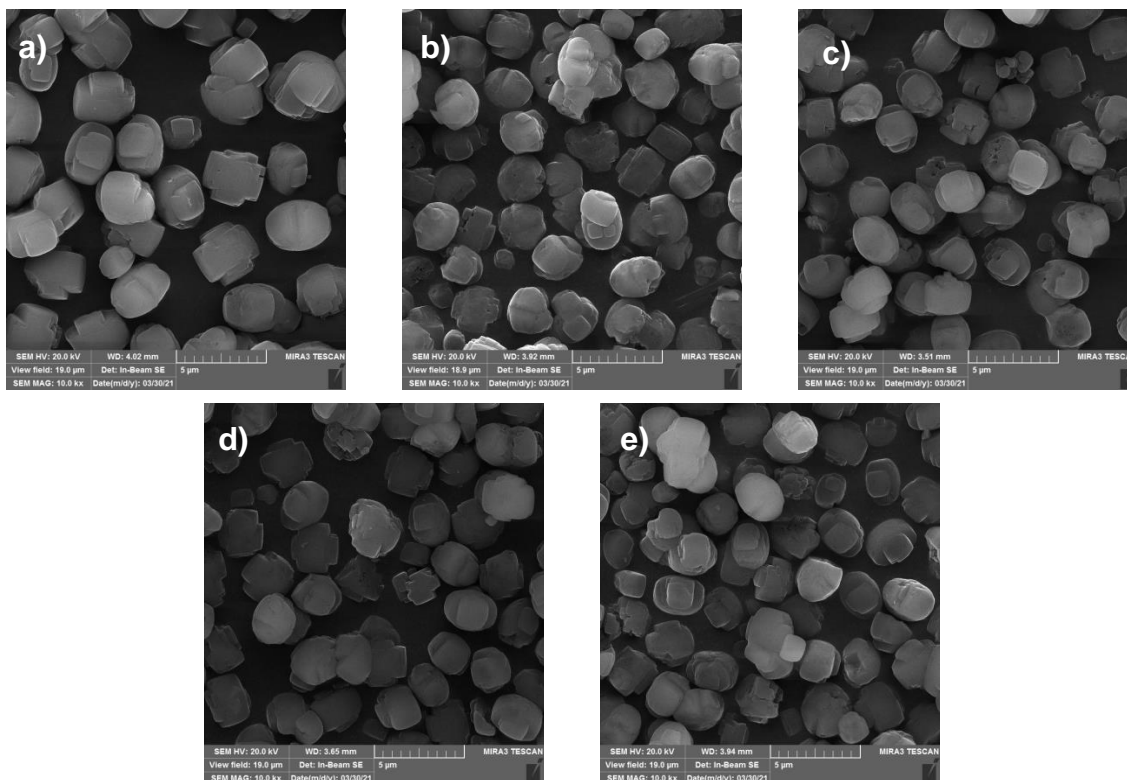


Figure 11. Results of SEM analysis: (a) non-calcined ZSM-5, (b) calcined ZSM-5, (c) ZSM-5 5% HCl 6h, (d) ZSM-5 10% HCl 3h, (e) ZSM-5 15% HCl 3h

Slika 11. Rezultati SEM analize: (a) nekalcinisanog ZSM-5, (b) kalcinisanog ZSM-5, (c) ZSM-5 5% HCl 6h, (d) ZSM-5 10% HCl 3h, (e) ZSM-5 15% HCl 3h

It is noticed that the application of 10% HCl (Figure 10) with increasing ion exchange time shifts the peaks to the right, which indicates the dominance of the process of partial decomposition of the crystal lattice, and binding of hydrogen ions to aluminium, where aluminium ions are separated from the zeolite structure. Also, with a decrease in the degree of crystallinity, the intensity of peaks in the range $2\theta = 22.7 - 25.1^\circ$ decreases (Table 3).

Based on the results presented in Figure 11, it can be observed that there are no significant changes in the morphological characteristics of ZSM-5 zeolite, neither by calcination nor by ion exchange with HCl [9, 21].

4. CONCLUSIONS

By reviewing the literature and analyzing the obtained results, it can be concluded that the ion exchange of zeolite ZSM-5 ($\text{SiO}_2/\text{Al}_2\text{O}_3 = 1000$) with hydrochloric acid can reduce the sodium content in the zeolite. Satisfactory results are achieved even with the 5% HCl, where during the ion exchange of 6 hours, the sodium content drops by 98% approximately, from 1.1% to 0.02%. On the other hand, by applying higher concentrations of acid, the same effect can be achieved in a shorter exchange time.

Apart from participating in ion exchange, hydrogen ions present also reduce the aluminium content at higher acid concentrations. Based on this, it can be observed that hydrogen ions have a dual effect on zeolites. On the one hand, they are exchanged with sodium ions, as a result of which zeolites of better acidic properties are obtained, which corresponds to their catalytic application in the processes of the petrochemical industry. The process of sodium ion exchange in ZSM-5 is dominant at lower concentrations of HCl (5% HCl and 7% HCl), due to which the change in aluminium content is insignificant. On the other hand, at acid concentrations higher than 7%, hydrogen ions bind to aluminium from the zeolite structure, which leads to certain defects of the crystal lattice of ZSM-5 zeolite. XRD diffractograms confirm the course of these two processes, where the characteristic peaks of ZSM-5 zeolite move along the 2θ axis, to the left (when the ion exchange reaction with sodium is dominant), and to the right (when the dealumination process is dominant, i.e. when the Al - O bond in the crystal lattice breaks).

The obtained values of the degree of crystallinity indicate a decrease in the crystallinity of calcined ZSM-5 compared to non-calcined zeolite due to increased aluminium content, which

in turn may be a consequence of removing templates and crystal water from the zeolite structure. In addition, the indicator of partial destruction of the crystal lattice, during ion exchange with HCl solutions of a higher concentration, is certainly a decrease in the degree of crystallinity.

The results obtained by FT-IR and SEM analyses, in combination with X-Ray diffraction, confirm the possibility of ion exchange with HCl, without significant defects in the crystal structure of ZSM-5 zeolite ($\text{SiO}_2/\text{Al}_2\text{O}_3 = 1000$). However, further investigations of the possibility of ion exchange of sodium with other, less aggressive acids are advised.

5. REFERENCES

- [1] J.Dedecek, V.Balgová, V.Pashkova, P.Klein, B.Wichterlová (2012) Synthesis of ZSM-5 zeolites with defined distribution of Al atoms in the framework and multinuclear MAS NMR analysis of the control of Al distribution, *Chemistry of Materials*, 24(16), 3231-3239.
- [2] V.Leone, P.Iovino, E.Coppola, S.Salvestrini, S.Capasso (2016) Sorption of organic pollutants onto zeolitic tuff, *Zastita materijala*, 57(4), 515-519.
- [3] Y. K.Rohayati, R.Sihombing (2017) Synthesis of ZSM-5 zeolite using Bayat natural zeolite as silica and alumina source, *AIP Conference Proceedings*, 1862 (1) p. 030094
- [4] R.T.Yang (2003) *Zeolites and Molecular sieves, in Adsorbents: Fundamentals and Applications*; Publisher: John Wiley & Sons, New Jersey, p. 157 – 190.
- [5] B. Jha, D.N.Singh (2016) Basics of zeolites, in *Fly Ash Zeolites*; Publisher: Springer, Singapore, p 5-31.
- [6] J. Weitkamp (2000) Zeolites and catalysis, *Solid state ionics*, 131(1-2), 175-188.
- [7] S.Wang, Y.Peng (2010) Natural zeolites as effective adsorbents in water and wastewater treatment, *Chemical engineering journal*, 156(1), 11-24.
- [8] F.Jin, Y.Fan, M.Yuan, F.Min, G.Wu, Y.Ding, G.F.Froment (2018) Single-event kinetic modeling of ethene oligomerization on ZSM-5, *Catalysis Today*, 316, 129-141.
- [9] L.Shirazi, E.Jamshidi, M.R.Ghasemi (2008) The effect of Si/Al ratio of ZSM-5 zeolite on its morphology, acidity and crystal size. *Crystal Research and Technology: Journal of Experimental and Industrial Crystallography*, 43(12), 1300-1306.
- [10] I. Díaz, E.Kokkoli, O.Terasaki, M.Tsapatsis (2004) Surface structure of zeolite (MFI) crystals. *Chemistry of materials*, 16(25), 5226-5232.
- [11] R.P.Townsend, E.N.Coker (2001) Ion exchange in zeolites, in *Studies in surface science and catalysis 137*; Publisher: Elsevier, Oxford, p. 467-524.

- [12] A.A.Zagorodni (2007) Ion exchangers, their Structure and Major Properties, in Ion Exchange Materials Properties and Applications, 1st edition; Publisher: Elsevier, Oxford, p 9 – 54.
- [13] C.Colella (1996) Ion exchange equilibria in zeolite minerals, *Mineralium Deposita*, 31 (6), 554-562.
- [14] S.O.Jevtić (2015) Sinteza i karakterizacija materijala nastalih modifikacijom prirodnog zeolita (klinoptilolita) i mikroporoznih fosfata sa strukturom zeolita (*Synthesis and characterization of materials obtained by modification of natural zeolite (clinoptilolite) and phosphate based microporous materials with zeolitic structure*), Doctoral Dissertation, Faculty of Technology and Metallurgy, Belgrade.
- [15] E.T.C.Vogt, G.T.Whiting, A.D.Chowdhury, B.M.Weckhuysen (2015) Zeolites and zeotypes for oil and gas conversion, *Advances in catalysis*, 58, 143-314.
- [16] T.Ma, L.Zhang, Y.Song, Y.Shang, Y.Zhai, Y.Gong (2018). A comparative synthesis of ZSM-5 with ethanol or TPABr template: distinction of Brønsted/Lewis acidity ratio and its impact on n-hexane cracking. *Catalysis Science & Technology*, 8(7), 1923-1935.
- [17] P.J.Danaher, C.Medino, H.Shevchuk, E.M.Zhang (2017) Testing the stability of cation exchanged zeolite ZSM-5 in hot liquid water, dostupno na: <https://digital.wpi.edu/downloads/gf06g4038> [Accessed: January 9, 2021]
- [18] K.Byrappa, B.V.Kumar (2007) Characterization of Zeolites by Infrared Spectroscopy, *Asian Journal of Chemistry*, 19(6), 4933-4935.
- [19] S.A.Paramadini, R.Ekananda, Y.K.Krisnandi (2019) Synthesis and characterization of ZSM-5 zeolite with micro-and hierarchical pore structures from Bayat natural zeolite, *IOP Conference Series: Materials Science and Engineering*, 496 (1), p 012022.
- [20] S.Creci, X.Wang, P.A.Carlsson, M. Skoglundh (2019) Tuned Acidity for Catalytic Reactions: Synthesis and Characterization of Fe- and Al-MFI Zeotypes, *Top Catal*, 62, 689–698.
- [21] A.S.Araujo, A.O.Silva, M.J.Souza, A.C.Coutinho, J.Aquino, J.A.Moura, A.M. Pedrosa (2005) Crystallization of ZSM-12 zeolite with different Si/Al ratio, *Adsorption*, 11(2), 159-165.

IZVOD

Jonska izmjena natrijuma sa hlorovodoničnom kiselinom na zeolitu zsm-5

ZSM-5 zeoliti su visokosilikatni materijali koji imaju značajnu primjenu kod katalitičkih procesa u petrohemiji, naročito zbog visoke selektivnosti. Većina reakcija u petrohemijskoj industriji je katalizovana kiselinama. Kiseliniska svojstva zeolita su zavisna od količine kiselih centara, odnosno prisustva vodoničnih jona, te će stoga, u ovom radu biti ispitana mogućnost smanjenja sadržaja natrijuma u porama visokosilikatnog zeolita ZSM-5 sa modulom ($\text{SiO}_2/\text{Al}_2\text{O}_3 = 1000$) primjenom procesa jonske izmjene sa hlorovodoničnom kiselinom. Hemijskom analizom uzoraka prije i poslije jonske izmjene, te primjenom instrumentalnih metoda X-Ray difrakcije, FT-IR spektroskopije i SEM analize praćen je uticaj količine vodoničnih jona na hemijski sastav i promjenu strukture ZSM-5 zeolita pri različitim koncentracijama kiseline, te različitim vremenima jonske izmjene.

Pokazano je da je primjenom jonske izmjene sa hlorovodoničnom kiselinom moguće smanjiti sadržaj natrijuma u zeolitu. Već pri primjeni 5% HCl u trajanju od 6 sati postiže se redukcija sadržaja natrijuma u zeolitu od preko 98%. Sličan efekat se postiže pri primjeni koncentrovanijih rastvora hlorovodonične kiseline za kraće vrijeme jonske izmjene. Produženjem vremena jonske izmjene, ne dolazi do znatnijih promjena u pogledu konačne jonske izmjene. S druge strane, primjena rastvora HCl većih koncentracija dovodi do blagog pada sadržaja aluminijuma u zeolitu, što može djelimično uticati na strukturnu stabilnost zeolita. Rezultati dobijeni FT-IR i SEM analizom, te X-Ray difrakcijom potvrđuju mogućnost jonske izmjene sa hlorovodoničnom kiselinom, bez značajnijih promjena kristalne strukture zeolita.

Ključne riječi: zeolit, jonska izmjena natrijuma, karakterizacija H-ZSM-5, XRD, FT-IR, SEM.

Naučni rad

Rad primljen: 14. 04. 2021.

Rad prihvaćen: 28. 05. 2021.

Rad je dostupan na sajtu: www.idk.org.rs/casopis