

Esraa Razaq<sup>1</sup>, Shaymaa Abbas Abdulsada<sup>2\*</sup>

<sup>1,2</sup>Department of Materials Engineering, Faculty of Engineering,  
University of Kufa, Iraq

Scientific Paper

ISSN 0351-9465, E-ISSN 2466-2585

<https://doi.org/10.62638/ZasMat1161>



Zastita Materijala 65 (4)

645 - 652 (2024)

## Effect of Corrosion Inhibitors on Internal Corrosion in Oil Pipelines: A Brief Review

### ABSTRACT

The oil and gas industry primarily relies on pipelines to transport crude and refined petroleum, so transportation of crude oil is mostly handled by pipelines. In view of this, it is impossible to prevent the pipeline surfaces from being continuously exposed to corrosion sources, such as contaminants that contain traces of chromate and sulfur, which can cause corrosion to occur on the pipeline surfaces. It is known that corrosion inhibitors are chemicals that are used in low concentrations for the purpose of reducing or preventing corrosion. The effectiveness of an inhibitor is determined by its ability to react with a metal's surface and produce a protective coating that reduces or prevents corrosion by reacting with the metal's surface. A review of corrosion mechanisms in oil pipelines is presented in this article, along with a description of how corrosion inhibitors can be selected according to the corrosion mechanisms in oil pipelines.

**Keywords:** Pipelines, Corrosion, Green inhibitors, Carboxylates, Oil.

### 1. INTRODUCTION

There is a natural tendency for materials, especially metals, to corrode when they react with their environment. Though the mechanisms by which this phenomenon occurs and the consequences that it causes may differ from one another, it is a phenomenon that affects both metallic and non-metallic materials. Corrosion of metallic materials, or rust, is the most common form of corrosion. Iron, in reaction with oxygen and moisture in the air, forms iron oxide (rust). Polymers, for instance, are affected by degradation, which is a type of corrosion. It is important to note that polymers can also degrade if exposed to UV radiation, heat, moisture, and chemicals, in addition to degradation caused by UV radiation, heat, moisture, and chemicals. Even though ceramics are chemically resistant, they may degrade in aggressive environments because of mechanical wear, thermal shock, and chemical attack, despite the fact that they are chemically resistant.

\* Corresponding author: Shaymaa Abbas Abdulsada

E-mail: shaymaa.radhi@uokufa.edu.iq

Paper received: 25.03.2024.

Paper accepted: 12.04.2024.

Paper is available on the website: [www.idk.org.rs/journal](http://www.idk.org.rs/journal)

The other type is concrete corrosion, as it is possible for steel reinforcement in reinforced concrete structures to corrode if it is exposed to corrosive chemicals, chloride ions, and carbonation over time. Due to this, the concrete may crack and crumble as a result [1-13]. As mentioned above, the corrosion of metal occurs as a result of chemical reactions between the metal and the environment around it, which causes the metal to slowly disintegrate over time as the environment around it changes [14,18]. As innovative gas fields develop, it is critical that we have the ability to move damp, unprocessed indigenous gases through pipelines and into other inaccessible areas in order to facilitate the advancement of these fields. The importance of understanding corrosion and the methods for preventing it, because of this, cannot be overstated both in terms of safety and economics. Due to the flow of oil inside pipelines, as well as the fact that the pipelines are buried underground, oil pipelines are exposed to internal corrosion as well as external corrosion due to the fact that they are buried underground [18-23].

The use of pipelines for oil and gas delivery is widely recognized as one of the most cost-effective and safest methods. It is still necessary to evaluate corrosion and develop the best mitigation techniques for carbon steel pipelines because they

are prone to corrosion. As one of the primary means of transporting oil and gas, pipelines have many advantages, including their low operating costs, quick and convenient operations, and capacity to transport large amounts of material. There are a number of pipelines around the world that are unfortunately subject to both internal and exterior corrosion, which could have a significant negative impact both economically and environmentally in the long run [21-26]. Oil pipelines transfer liquid petroleum products from one location to another. There are four types of oil pipelines, (1) gathering pipelines, which transport oil over short distances with pipe diameters ranging from

10.2 to 30.2 cm, (2) feeder pipelines, which transport oil product from oil storage tanks or processing plants to gearbox pipelines and are typically larger than gathering lines. (3) transmission pipelines, in addition to the smaller diameter pipelines, these are also used for transporting oil and natural gas over longer distances; between provinces or countries, and (4) distribution lines can be up to 122 cm in diameter and deliver crude oil from production to export or consumption points. Corrosion in crude oil pipelines is one of the most serious issues related

with the presence of water and contaminants such as chlorides, sulphates,  $\text{CO}_2$ , and  $\text{H}_2\text{S}$  dissolved gases. One method for preserving interior oil pipes from corrosion is to use corrosion inhibitors [27-28].

Corrosion inhibitors are one of the methods used to reduce corrosion in petroleum industry. To ensure optimum inhibition, the inhibitors must be supplied at concentrations greater than a particular minimum. There are numerous techniques for combating corrosion, such as cathodic protection, organic coatings, and the use of high-quality corrosion-resistant alloys, but film-forming inhibitors are still widely regarded as the unrivalled method of defence for mild steel in an acid environment. Film-forming inhibitors are used in industries to build a molecular layer directly on the steel surface and an aliphatic tail as a second layer of hydrocarbon to prevent water from touching the steel surface and causing corrosion. All forms of internal corrosion that are anticipated to occur in pipelines are schematically summarised in Fig. 1 to aid in understanding of the various forms of internal corrosion caused by metal loss or cracking mechanism, which will be covered in more detail later [29-43].

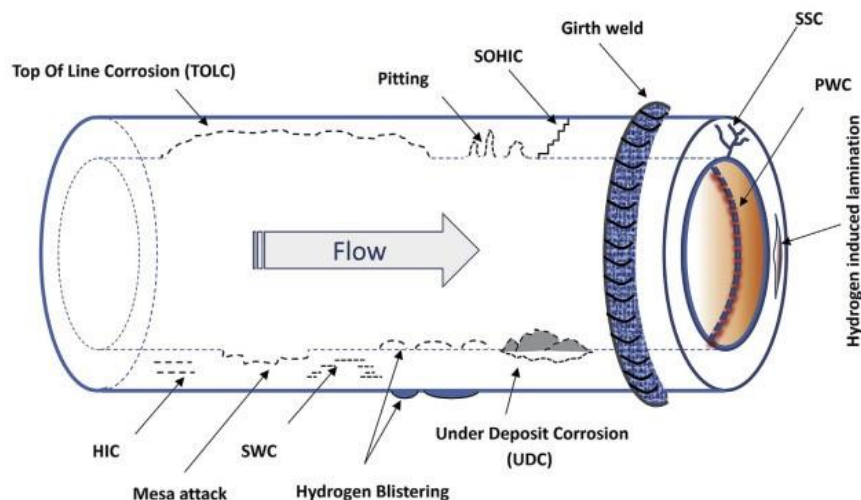


Figure 1. Various types of internal pipeline corrosion in hydrocarbons [43]

## 2. CAUSES OF OIL FIELD CORROSION

In oil fields, corrosion can often be traced back to the use of drilling fluids that penetrate into the crude oil that is going to be transported later in the process. These fluids include all of the following [44]:

- In certain sectors, organic acids are also present, such as acetic acid, which can cause  $\text{CO}_2$  containing devices to corrode faster compared to others. There are hydrocarbon phases; oils with different compositions; and gases like ethane and methane.
- There are dissolved salts such as calcium carbonate, barium sulphate, sodium sulphate, and sodium chloride in the produced water, which can induce scaling. Water injection can cause water breakout and souring, as well as scaling due to chemical mixing and hydrogen sulfide generation.
- There are several acids that can dissolve in water and generate corrosive electrolytes, such as carbon dioxide and hydrogen sulphide, which can produce acidic gases.

### 3. CORROSION MECHANISM IN OIL PIPELINES

Metal corrosion can be considered as an environmental element that is characterised as the unintentional destruction and degradation of working pipelines in an internal or external environment, as a result of chemical, electrochemical, or biochemical contact with the environment. The process of corrosion, which occurs when chemical or electrochemical reactions occur during the interaction between metallic materials and the environment, is a deteriorating attack on metallic materials. Fig. 2 depicts some types of rusting [45].



Figure 2. Different forms of Corrosion [45]

As far as corrosion in oil and gas refineries and related industries is concerned, there are a number of different forms of corrosion that occur in these facilities. These include microbiologically induced corrosion, erosion, stress corrosion cracking, crevice corrosion, oxygen corrosion, sweet corrosion, and sour corrosion [46]. The material of the pipeline has a significant impact on pipeline corrosion as well.

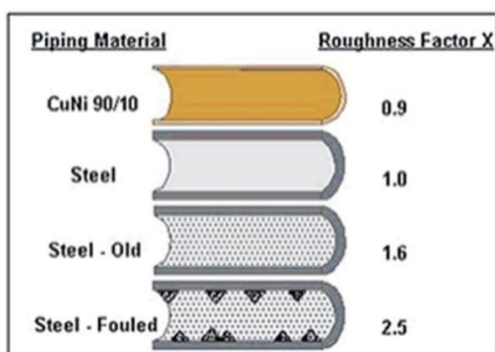


Figure 3. Selection of Piping Materials [47]



The piping material with its varying roughness is shown in Fig. 3. Certain materials, like steel or steel concrete, will increase the rate of corrosion in the pipeline, while other materials, like PVC,

stainless steel, and some special alloys, can extend the lifespan of the pipeline [47].

### 4. CORROSION INHIBITORS IN OIL PIPELINES

An inhibitor is a chemical that, when introduced in modest doses, reduces the effective corrosion rate. Inhibitors are classified into four categories based on their mechanism and content. The four categories are barrier layer development, neutralising, scavenging, and environmental change. Temperature and water chemistry are two elements that can influence the blockage of petroleum pipelines [44]. Organic compounds are commonly utilised as corrosion inhibitors in oil field applications, where they are applied in modest amounts (less than 0.1%). Because they adsorb on the steel surface and inhibit both the anodic and cathodic reactions, they are frequently classed as mixed inhibitors. Nonetheless, a lot of inhibitor packages that are sold commercially have a tendency to polarise the steel anodically. Known as filmmaking inhibitors, oilfield corrosion inhibitor chemicals also push adsorbed water molecules away from the surface. For instance, jet fuel, a product with a low water content, uses inhibitor compounds, which only function in this way. Nearly all organic molecules used in oil field corrosion inhibitor packages are strongly polar functional compounds, many of which have a nitrogen basis, such as amines, amides, imidazolines, or quaternary ammonium salts. These compounds also include compounds containing P, S, and O, nitrogen heterocyclics, polyoxyalkylated nitrogen-containing compounds, and salts of nitrogenous molecules with carboxylic acids.

Table 1: Fundamental chemical structures of inhibitors used in oilfields [48]

| Chemical name           | Structure   |
|-------------------------|---|
| Primary amine           | $R-CH_2-NH_2$   |
| Amide                   | $R_1-CH_2-C(=O)-NH-R_2$   |
| Imidazoline             |  |
| Quaternary ammonium ion |  |
| Polyethoxylated amines  | $R-N\left(\begin{matrix} (O-CH_2-CH_2)_n \\ (O-CH_2-CH_2)_n \end{matrix}\right)-OH$   |

It is frequently disputed whether species in the package actually offers protection because, for





### Carboxylates

By forming a hydrophobic coating on the metal surface through the adsorption of a carboxylate group (Lewis base) on Lewis acid, carboxylates can offer corrosion protection. While short-chain fatty acids may encourage corrosion, long-chain fatty acids—like oleic acid, soy fatty acid, TOFA, and polymerized fatty acids—like dimer acids, have long been known to reduce corrosion in a variety of applications. Dicarboxylic acid and its derivatives, known as dicarboxylic esters, have been researched as useful additives for stopping metal corrosion in compositions. Rust development in lubricating oils can be effectively reduced by a synergistic combination of amine derivatives derived from succinic anhydride and tetrapropenyl succinic acid. It should be mentioned, though, that the dicarboxylic acids have a propensity to precipitate when  $\text{Ca}^{2+}$  or  $\text{Mg}^{2+}$  ions are present, which would negate their ability to prevent rust [53]. However, an outer negative surface can be generated by carboxylates, and it is possible that the amine carboxylate based inhibitors, Fig. 5, could form a film on the steel surface by associating nitrogen with iron atoms. Consequently, a repulsive force between the carboxylate and the chloride in the media or environment is created. The repelling force is significant at low concentrations of chloride and sulphate, but it becomes less at higher concentrations. Therefore, it is probable that sulphate or chloride seeped into the steel, which is why the film's efficiency decreased [54].

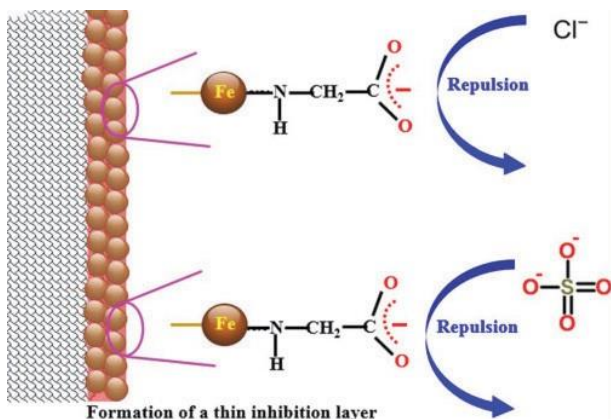


Figure 5. Proposed mechanisms for the inhibition of corrosion of carbon steel by the investigated aminecarboxylate based inhibitors [54].

### Amines

Film-forming amines, or fatty amines, are fatty acid derivatives. These components, which have poor alkaline characteristics, have been neutralised by the use of organic acids in the formulation of the corrosion inhibitor or by the action of acid gases in the fluid, converting them to cationic

components with positive charges. Because electrons are re-released on the cathode as a result of corrosion, these cationic components are attached to the cathode and form an oily coating on the metal's surface, preventing acid gases from contacting the cathode while releasing hydrogen. Corrosion inhibitors are classified into functional groups with polar heads, such as fatty acids, amines, imidazoline, oxyalkylated amines, oxygen, sulphur, or phosphorus, and quaternary amine salts. Furthermore, corrosion inhibitors with a long chain of hydrocarbons (typically C14-C18) cling well to the surface [55].

### 5. CONCLUSION

Overall, it can be concluded that corrosion is an issue of great importance in the oil and gas industry, particularly the pipeline industry, where it can lead to economic losses as well as environmental damage. It is critical to ensure pipeline integrity and safety by understanding the mechanisms of corrosion and applying effective mitigation techniques, such as the use of corrosion inhibitors, in order to prevent corrosion in oil pipelines. A variety of corrosion inhibitors are available, including green inhibitors, organic inhibitors, inorganic inhibitors, carboxylates, and amines, and each of them has its own unique protective mechanism for preventing corrosion in pipelines. The key to successful corrosion prevention is selecting the right inhibitor based on the conditions in the environment and the type of system being treated. It is vital that the oil and gas sector uses corrosion inhibitors and follows regular maintenance methods in order to ensure safe and efficient transportation of oil and gas through pipelines.

### 6. REFERENCES

- [1] A. Groysman (2009) Corrosion phenomena. In Springer eBooks, 53–108. [https://doi.org/10.1007/978-90-481-3477-9\\_2](https://doi.org/10.1007/978-90-481-3477-9_2)
- [2] A. A. Shaymaa (2014) Corrosion Inhibitors: Principles and Applications, 1<sup>st</sup> Edition, LAP LAMBERT Academic Publishing, Germany.
- [3] J. K. B. Balangao (2024) Corrosion of Metals: factors, types and prevention Strategies. J. Chem. Hea. Ri., 14, 79-87. <https://jchr.org/index.php/JCHR/article/view/2120>
- [4] T. W. Quadri, E. D. Akpan, L. O. Olasunkanmi, O. E. Fayemi, E. E. Ebenso (2022) Fundamentals of corrosion chemistry. In Elsevier eBooks, 25–45. <https://doi.org/10.1016/b978-0-323-85405-4.00019-7>
- [5] S. Zehra, M., Mobin, R. Aslam (2022) Corrosion prevention and protection methods. In Elsevier eBooks, 13–26. <https://doi.org/10.1016/b978-0-323-91176-4.00023-4>

- [6] A.I. Al-Mosawi, K. Marossy (2020) Elimination of plasticized poly(vinyl chloride) degradability by using oxydtron: a novel study, *ARPN J. Eng. App. Sci.*, 15, 405-411.
- [7] S. Pyun, (2020). Strategies of metal corrosion protection. *ChemTexts*, 7, 1. <https://doi.org/10.1007/s40828-020-00121-y>
- [8] A.I. Al-Mosawi (2021) A novel evaluation method for dehydrochlorination of plasticized Poly(vinyl chloride) containing heavy metal-free thermal stabilizing syner-gistic agent. *Poly. Adv. Tech.*, 32, 3278–3286. <https://doi.org/10.1002/pat.5339>
- [9] B. A. Omran, M. O. Abdel-Salam (2020) Basic corrosion Fundamentals, aspects and currently applied strategies for corrosion mitigation. In *Adv. mat. rese. tech.*, 1–45. [https://doi.org/10.1007/978-3-030-49532-9\\_1](https://doi.org/10.1007/978-3-030-49532-9_1)
- [10] A. I. Al-Mosawi (2021) A new generation of cable grade poly(vinyl chloride) containing heavy metal freemodifier. *J. Poly. Res.*, 29, 9. <https://doi.org/10.1007/s10965-021-02798-2>
- [11] P. Pedefferri (2018) Corrosion in concrete. In *Engineer-ing materials*, 509–548. [https://doi.org/10.1007/978-3-319-97625-9\\_23](https://doi.org/10.1007/978-3-319-97625-9_23)
- [12] A. I. Al-Mosawi, S. A. Abdulsada (2022) Enhancement of thermal characteristics of flexible poly(vinyl chloride) for automotive applications by using environmentally friendly heavy metal-free modifier. *Journal of Thermoplastic Composite Materials*, 36, 3383–3402. <https://doi.org/10.1177/08927057221129488>
- [13] E.J. Opila, N. S. Jacobson (2013) Oxidation and Corrosion of Ceramics, In: Riedel, R., Chen, I. (eds.) *Ceram. Sci. Tech.*, Wiley-VCH Verlag GmbH & Co. KgaA,. <https://doi.org/10.1002/9783527631971.ch01>
- [14] J. K. Al-Kafaji and A.I. Al-Mosawi (2014) Adding hydrazine to pigments to prevent corrosion of ferrous alloys, *University of Kerbala Journal, Special Issue for 2<sup>nd</sup> scientific conference, science College, University of Kerbala, Iraq*. <https://doi.org/10.6084/m9.figshare.19180982>
- [15] S. A. Abdulsada, A. I. Al-Mosawi (2022) Corrosion behaviour and surface topography for steel plates used in automotive industry exposed to salty corrosive thermo-accelerated medium. *Épít.*, 74. <https://doi.org/10.14382/epitoanyag-jsbcm.2022.31>
- [16] S. A. Abdulsada, A. I. Al-Mosawi and A.A. Hadi (2017) Studying the effect of eco-addition inhibitors on corrosion resistance of reinforced concrete, *Bio. Eng.*, 1, 81-86. <https://doi.org/10.11648/j.be.20170103.14>
- [17] S. A. Abdulsada, A. I. Al-Mosawi (2023) Analysis of corrosion rate, inhibition efficiency, and economic cost of XD3 reinforced concrete related to inhibitor and plasticiser types, *Eng. Res. Exp.*, 5, 035032. <https://doi.org/10.1088/2631-8695/acee46>
- [18] Z. Albaraqaawee, S. A. Abdulsada, A. I. Al-Mosawi (2024) Analysis of coated samples containing hydroxyapatite/multiwalled carbon nanotubes on 2205 DSS substrate, *Full., Nano. C. Nano.*, 2024. <https://doi.org/10.1080/1536383X.2024.2309943>
- [19] D. S. Freitas (2023) Mechanisms of Corrosion of Pipelines, In: *ABCM - Brazilian Society of Mechanical Sciences and Engineering, de França Freire, J.L., Rennó Gomes, M.R., Guedes Gomes, M. (eds.) Handbook of Pipeline Engineering*. Springer, Cham. [https://doi.org/10.1007/978-3-031-05735-9\\_29-1](https://doi.org/10.1007/978-3-031-05735-9_29-1)
- [20] K. Tamalmani, H. Husin (2020) Review on Corrosion Inhibitors for Oil and Gas Corrosion Issues. *Appl. Sci.*, 10, 3389. doi :10.3390/app10103389
- [21] X.X. Chen, Y. Zhao (2017) Research on Corrosion Protection of Buried Steel Pipeline. *Eng.*, 9, 504-509. doi:10.4236/eng.2017.95030
- [22] X. Lei (2024) Visualization and Analysis of Oil and Gas Pipeline Corrosion Research: A Bibliometric Data-Mining Approach, *J. Pip. Syst. Eng. Pract.*, 15. <https://doi.org/10.1061/JPSEA2.PSENG-160>
- [23] Y. Frank Cheng (2015) Pipeline corrosion, *Corr. Eng. Sci. Tech.*, 50, 161-162. <https://doi.org/10.1179/1478422X15Z.000000000357>
- [24] M. Amin (2021) Corrosion Investigation of an Oil and Gas Pipe Section and Prediction of its Future Performance. *University of British Columbia, Vancouver, BC, Canada*. 05.
- [25] D. S. Freitas, A. M. Silva, I. L. M. Gonçalves (2023) Mechanisms of Corrosion of Pipelines, In: *França Freire, J. L., Rennó Gomes, M. R., Guedes Gomes, M. (eds.) Handbook of Pipeline Engineering*. Springer, Cham. [https://doi.org/10.1007/978-3-031-05735-9\\_29-1](https://doi.org/10.1007/978-3-031-05735-9_29-1)
- [26] C. M. Silva, M. C. Barreto, W. G. Castinheiras (2023) Pipeline Corrosion Management. In: *França Freire, J.L., Rennó Gomes, M.R., Guedes Gomes, M. (eds.) Handbook of Pipeline Engineering*. Springer, Cham. [https://doi.org/10.1007/978-3-031-05735-9\\_30-1](https://doi.org/10.1007/978-3-031-05735-9_30-1)
- [27] H. H. Jasim, R. A. Al-Hussain (2019) Evaluation of Inhibitor Efficiency in Crude Oil Pipeline of Missan OilFields South Iraq. *J. Eng. Sust. Devel.*, 23.
- [28] Pipeline 101 – Four Different Types of Pipelines, *Technical Report, Energy Connections Canada*, 2023.
- [29] A. A. Shaymaa, R. Bak, A. Heczal, I.T. Tamás (2020) Corrosion studies on XD3 reinforced concrete samples prepared by using calcium nitrate as inorganic corrosion inhibitor with different superplasticizers, *KOM – Corr. Mat. Prot. J.*, 64, 11-18, <https://doi.org/10.2478/kom-2020-0002>

- [30] A. A. Shaymaa, I.T. Tamás (2020) Studying chloride ions and corrosion properties of reinforced concrete with a green inhibitor and plasticizers, *Str. Con.*, 21, 1894-1904, <https://doi.org/10.1002/suco.201900580>
- [31] A. A. Shaymaa, I.T. Tamás (2020) Investigations on the resistivity of XD3 reinforced concrete for chloride ions and corrosion with calcium nitrate inhibitor and superplasticizers, *Cem.Wap. Bet.*, 25, 330-343, <https://doi.org/10.32047/cwb.2020.25.4.7>
- [32] A. A. Shaymaa, K. Ferenc, I. T. Tamás (2020) Distribution of corrosion products at the steel-concrete interface of XD3 concrete samples, *Mag. Civ. Eng.*, 100, 10005, <https://doi.org/10.18720/MCE.100.5>
- [33] A. A. Shaymaa, A.I.Al-Mosawi (2016) Using of nucleated waste with a nanoscale particles as a green inhibitor, *Int. J. Mech. & Mech. Eng. IJMME-IJENS*, 16, 27–32.
- [34] A.Shaymaa, F.Éva, I.Tamás (2019) Corrosion testing on steel reinforced XD3 concrete samples prepared with a green inhibitor and two different superplasticizers, *Mat. Corr.*, 70, 1262-1272, <https://doi.org/10.1002/maco.201810695>
- [35] M. Tweek, S. Abdulsada (2023) Improvement corrosion properties of reinforcement concrete by corrosion inhibitors: A brief review. *KOM–Corr. Mat. Prot. J.*, 67, 50-58. doi: 10.2478/kom-2023-0007
- [36] M. Alam, M. Alandis, N. Ahmad, M.Alam (2018) Corrosion Protection of Carbon Steel by Pongamia glabra Oil-Based Polyetheramide Coatings, *Int. J. Elect.I Sci.*, 13, 3124-3135. doi:10.20964/2018.03.52
- [37] W. Chengduan, L. Chuan (2018) Corrosion inhibition of mild steel in HCl medium by S-benzyl-O, O'-bis(2-naphthyl) dithiophosphate with ultra-long lifespan. *Results Phys.* 10, 558–567. doi: 10.1016/j.rinp.2018.07.002
- [38] T. Salman, K.Al-Azawi, I.Mohammed, S.Al-Baghdadi, A.Al-Amiery, T.Gaaz (2018) Experimental and quantum chemical simulations on the corrosion inhibition of mild steel by 3-((5-(3,5-dinitrophenyl)-1,3,4-thiadiazol-2-yl) imino) indolin-2-one. *Results Phys.*, 10, 291–296. doi: 10.1016/j.rinp.2018.02.055
- [39] N. Odewunmi, S. Umoren, Z. Gasem, S. Ganiyu, Q. Muhammad (2015) Electrochemical and quantum chemical studies on carbon steel corrosion protection in 1 M H<sub>2</sub>SO<sub>4</sub> using new eco-friendly Schiff basemetal complexes. *J. Taiwan Inst. Chem. Eng.*, 51, 177–185. doi:10.1016/j.jtice.2015.12.021.
- [40] A. Zeino, A. Khaled, Jawich, M.; Obot, I. A. Ismail, H. M. Irshad, A. Zeino, I. H. Toor (2019) Electrochemical Corrosion Performance of Aromatic Functionalized Imidazole Inhibitor Under Hydrodynamic Conditions on API X65 Carbon Steel in 1 M HCl Solution. *Ara. J. Sci. Eng.* 44, 5877–5888. doi: 10.1007/s13369-019- 03745-6
- [41] S. Umoren, U. Eduok (2016) Application of carbohydrate polymers as corrosion inhibitors for metal substrates in different media: A review. *Carbohydr. Polym.* 140, 314–341. doi:10.1016/j.carbpol.2015.12.038
- [42] D. Yadav, B. Maiti, M. Quraishi (2010) Electrochemical and quantum chemical studies of 3,4-dihydropyrimidin-2(1H)-ones as corrosion inhibitors for mild steel in hydrochloric acid solution. *Corros. Sci.*, 52, 3586–3598.
- [43] M. Askari, M. Aliofkhaezaei, S. Afroukhteh (2019) A comprehensive review on internal corrosion and cracking of oil and gas pipelines, *J. Nat. Gas Sci. Eng.*, 71, 102971. doi:10.1016/j.jngse.2019.102971
- [44] Mark E. Orazem (2014) *Underground pipeline corrosion Detection, analysis and prevention*, Woodhead Publishing Series in Metals and Surface Engineering: Number 63.
- [45] J. Joseph P. Akpan, O Udom, F. John (2023) Oil and Gas Pipeline Corrosion Monitoring and Prevention Techniques in The Niger Delta Region, Nigeria: A Re-view. *J. Res. Eng.Com. Sci.*, 1, 43-54. <https://hspublishing.org/JRECS/article/view/114>
- [46] U. Bharatiya, P. Gal, A. Agrawal, M. Shah, A. Sircar (2019) Effect of Corrosion on Crude Oil and Natural Gas Pipeline with Emphasis on Prevention by Ecofriendly Corrosion Inhibitors: A Comprehensive Review. *J. Bio- and Tribo-Corr.* 5(2), 1-12, doi:10.1007/s40735-019-0225-9
- [47] T. Nagalakshmi, A. Sivasakthi (2019) Corrosion Control, Prevention and Mitigation in Oil & Gas Industry, *Int. J. Inno. Tech. Exp. Eng.*, 9, 1568-1572. doi:10.35940/ijitee.B7272.129219
- [48] A. J. McMahon, S. Groves (1995) *Corrosion Inhibitor Guidelines*, BP Sunbury report No.ESR.95.ER.050.
- [49] S. Webster, A. J. McMahon, D. M. E. Paisley, D. Harrop (1996) *Corrosion Inhibitor Test Methods*, BP Sunbury Report No. ESR 95.ER.054.
- [50] F. Hameed, H. Rashida, A. Khadomb (2022) New Developments in Inhibition of the Sweet Environment in a Variety of Corrosive Media: A Review. *Eng. Tech. J.*, 40, 1117- 113. doi:10.30684/etj.2022.132127.1093
- [51] B. E. Brycki, I. H. Kowalczyk, A. Szulc. (2018) Organic corrosion inhibitors. *Corrosion inhibitors, principles and recent applications*, Ch.1, 3-33. doi: 10.5772/in-techopen.72943.
- [52] K. Tamalmani H. Husin (2020) *Review on Corrosion Inhibitors for Oil and Gas Corrosion*, Department of Petroleum Engineering, Universiti Teknologi PETRO-NAS, Bandar Seri Iskandar 32610, Perak, Malaysia.

- [53] Z. Tang (2017) A review of corrosion inhibitors for rust preventative fluids, NTIC (Shanghai) Co., Ltd., Shanghai, China.
- [54] K. A. Al-Sodani, M. Maslehuddin, O.S. Al-Amoudi (2018) Efficiency of generic and proprietary inhibitors in mitigating Corrosion of Carbon Steel in Chloride-Sulfate Environments. Sci Rep 8, 11443. <https://doi.org/10.1038/s41598-018-29413-7>
- [55] M. Askari, M. Aliofkhazraei, S. Ghaffari, A. Hajizadeh (2018) Film Former Corrosion Inhibitors for Oil and Gas Pipelines - A Technical Review, J. Nat. Gas Sci. & Eng., 2, <https://doi.org/10.1016/j.jngse.2018.07.025>

## IZVOD

### EFEKAT INHIBITORA KOROZIJE NA UNUTRAŠNJU KOROZIJU U NAFTOVODIMA: KRATAK PREGLED

*Industrija nafte i gasa se prvenstveno oslanja na cevovode za transport sirove i rafinisane nafte, tako da se transport sirove nafte uglavnom obavlja cevovodima. S obzirom na ovo, nemoguće je sprečiti da površine cevovoda budu kontinuirano izložene izvorima korozije, kao što su zagađivači koji sadrže tragove hromata i sumpora, koji mogu izazvati pojavu korozije na površinama cevovoda. Poznato je da su inhibitori korozije hemikalije koje se koriste u niskim koncentracijama u svrhu smanjenja ili sprečavanja korozije. Efikasnost inhibitora je određena njegovom sposobnošću da reaguje sa površinom metala i stvori zaštitni premaz koji smanjuje ili sprečava koroziju reagujući sa površinom metala. U ovom članku je dat pregled mehanizama korozije u naftovodima, uz opis načina izbora inhibitora korozije prema mehanizmima korozije u naftovodima.*

**Ključne reči:** cevovodi, korozija, zeleni inhibitori, karboksilati, nafta.

*Naučni rad*

*Rad primljen: 25.03.2024.*

*Rad prihvaćen: 12.04.2024.*

*Rad je dostupan na sajtu: [www.idk.org.rs/casopis](http://www.idk.org.rs/casopis)*

The ORCID Ids of all the authors are as follows:

1. Shaymaa Abbas: <https://orcid.org/0000-0001-7006-2950>

2. Esraa Razaq: <https://orcid.org/0009-0008-3963-4349>